



# Band-Bending Effect of Low-Temperature GaAs on a Pseudomorphic Modulation-Doped Field-Effect Transistor

W. D. Sun, Fred H. Pollak, Patrick A. Folkes, and Godfrey A. Gumbs

ARL-TR-1933

March 1999

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

Destroy this report when it is no longer needed. Do not return it to the originator.

# Army Research Laboratory

Adelphi, MD 20783-1197

---

ARL-TR-1933

March 1999

## Band-Bending Effect of Low-Temperature GaAs on a Pseudomorphic Modulation-Doped Field-Effect Transistor

W. D. Sun, Fred H. Pollak

Brooklyn College, City University of New York

Patrick A. Folkes

Sensors and Electron Devices Directorate, ARL

Godfrey A. Gumbs

Hunter College, City University of New York

---

---

## Abstract

---

Low-temperature photoluminescence (PL) measurements on pseudomorphic modulation-doped transistors with a low-temperature (LT) GaAs layer in the GaAs buffer layer clearly show a decrease in the quantum-well/PL transition energies compared to a structure with no LT GaAs. Self-consistent calculations of the electron and hole band structure confirm that the observed increase in the redshift in PL energies with increasing quantum-well/LT-GaAs spacing can be attributed to band bending induced by the Fermi level pinning at the undoped-GaAs/LT-GaAs interface.

# Contents

<b>Introduction</b> .....	<b>1</b>
<b>Experimental Results</b> .....	<b>2</b>
<b>Theory</b> .....	<b>4</b>
<b>Conclusion</b> .....	<b>6</b>
<b>Acknowledgement</b> .....	<b>6</b>
<b>References</b> .....	<b>7</b>
<b>Distribution</b> .....	<b>9</b>
<b>Report Documentation Page</b> .....	<b>13</b>

## Figures

1. PL spectra from structure with no LT GaAs and structures with QW/LT-GaAs spacing of 0.3, 0.8, and 1.6 $\mu\text{m}$ .....	3
2. Calculated and experimental $11H$ and $21H$ PL energies as a function of electric field in NID GaAs .....	5

# Introduction

Recently there has been much interest in the properties [1], device applications [2,3], and mechanism [4–8] of high-resistivity low-temperature GaAs (LT GaAs), which is grown by molecular beam epitaxy with a substrate temperature of around 200 to 300 °C. LT GaAs contains a high concentration of arsenic antisite defects ( $\text{As}_{\text{Ga}}$ ), which act as nonradiative recombination centers [5–7]. Consequently, LT GaAs exhibits a weak photoluminescence (PL) [1] and a subpicosecond electron-hole recombination time [9]. Recently we published the results of LT PL measurements on a number of pseudomorphic high-electron-mobility transistor (PHEMT) structures, which have an LT-GaAs layer embedded in the nominally undoped GaAs buffer layer at various depths below the quantum well (QW) [10]. Our results clearly showed a decrease in the PL energy (redshift) of the PHEMTs with LT GaAs, due to the quantum-confined Stark effect [11] and a novel band-bending effect of LT GaAs.

In this report we present the results of self-consistent modeling of this band-bending effect for the PHEMT structures, taking into account the Fermi level pinning at the interface between the normal-temperature not intentionally doped (NID) GaAs and the LT GaAs. Calculations of the electron and hole subband energies indicate that the redshift (decrease) in PL energy, which increases with the LT-GaAs/QW separation, can be explained by the variations in the electric field in the NID GaAs due to pinning of the Fermi level at the NID-GaAs/LT-GaAs interface.

# Experimental Results

The PHEMTs used in this study were grown by molecular beam epitaxy on semi-insulating GaAs. The PHEMT heterostructure consists of the following layers:

- 4000 Å of NID GaAs grown at 600 °C,
- 4000 Å of LT GaAs grown at 220 °C,
- a layer of NID GaAs grown at 600 °C whose thickness  $d$  varies for different samples,
- 150 Å of  $\text{In}_{0.2}\text{Ga}_{0.8}\text{As}$ ,
- 50 Å of undoped  $\text{Al}_{0.3}\text{Ga}_{0.7}\text{As}$ ,
- 100 Å of Si-doped ( $6 \times 10^{18} \text{ cm}^{-3}$ )  $\text{Al}_{0.25}\text{Ga}_{0.75}\text{As}$ ,
- 200 Å of undoped  $\text{Al}_{0.25}\text{Ga}_{0.75}\text{As}$ , and
- 200 Å of Si-doped ( $2 \times 10^{18} \text{ cm}^{-3}$ ) GaAs.


A control PHEMT was grown without any LT GaAs; instead it has a 1- $\mu\text{m}$  NID-GaAs buffer, which was grown at 600 °C. Note that the LT GaAs is annealed by the growth of the subsequent layers at 600 °C. Sheet resistance and Shubnikov-de Haas (SdH) measurements show that the two-dimensional electron gas (2DEG) density  $n_s$  and drift mobility are not degraded by the inclusion of the LT GaAs in the buffer, in agreement with previous results [12]. At 300 K, the measured  $n_s$  is  $1.9 \times 10^{12} \text{ cm}^{-2}$ , and the measured electron mobility is  $6000 \text{ cm}^2/\text{Vs}$ . The 2DEG mobility at 4.2 K for the PHEMTs with LT GaAs ranges from  $2.7 \times 10^4$  to  $8.3 \times 10^4 \text{ cm}^2/\text{Vs}$ . The SdH measurements also confirm that the  $n = 2$  conduction subband of the InGaAs QW is occupied for all samples. The measured electron density in the second subband is  $1 \times 10^{11} \text{ cm}^{-2}$  for the structure with no LT GaAs and approximately  $2 \times 10^{11} \text{ cm}^{-2}$  for the structures with LT GaAs. PL measurements were carried out with the samples mounted in a variable-temperature liquid helium cryostat. The 5145-Å emission from an argon ion laser was used to excite the structures with excitation intensity of about  $1 \text{ W}/\text{cm}^2$ . The PL spectrum was measured with a 1-m monochromator and a germanium photodetector.

Figure 1 shows the 5.8 K PL spectra for structures with QW/LT-GaAs spacings of 0.3, 0.8, and 1.6  $\mu\text{m}$  and for the structure with no LT-GaAs layer. The observed PL spectrum of the sample without the LT GaAs at 5.8 K shows a 16-meV-wide (full width at half maximum) asymmetric feature having a peak at 1255 meV, and a relatively sharp feature at 1315 meV having a width of 3 meV and an integrated PL intensity that is a factor of approximately 3 greater than that of the 1255-meV peak. Two observations—the difference between the low-energy and the high-energy peaks and the dependence of the PL on the electric field of the NID-GaAs buffer layer—lead us to conclude that the observed PL can be attributed to the recombination of  $n = 1$  and  $n = 2$  subband electrons from

the degenerate 2DEG with  $m = 1$  heavy holes in the InGaAs QW. The low-energy PL feature (designated  $11H$ ) is attributed to the transition of  $n = 1$  electrons to  $m = 1$  heavy holes. The high-energy PL feature (designated  $21H$ ) is attributed to the transition of  $n = 2$  electrons to  $m = 1$  heavy holes. The width of the  $11H$  PL feature is broadened by indirect recombination processes, which are facilitated by the scattering of carriers in the QW by ionized impurities in the doped AlGaAs barrier [13]. The relatively large peak intensity, sharp symmetric lineshape, and narrow width of the  $21H$  PL feature suggest that this feature has a strong component from the recombination of  $n = 2$  subband excitons.

These data show that the structures with an LT-GaAs layer exhibit a redshift in their PL transition energies. The  $11H$  and  $21H$  PL energies decrease with increasing QW/LT-GaAs spacing  $d$ , for spacings up to  $1.6 \mu\text{m}$ . Note that the shift in transition energy seems to approach an asymptote at  $d \approx 1.6 \mu\text{m}$ , as shown in figure 1. When the structure with  $d = 1.6$  is compared to the structure without LT GaAs, the observed redshifts of the  $11H$  and  $21H$  PL energies are  $17.3$  and  $21.7$  meV, respectively. Figure 1 shows that for structures with an LT-GaAs layer, the  $21H$  PL lineshape is asymmetric with a linewidth of  $\approx 6.2$  meV, compared to a linewidth of  $3$  meV for the sample without LT GaAs. In contrast, the width and line shape of the  $11H$  PL are the same for all the structures.

**Figure 1.** PL spectra from structure with no LT GaAs and structures with QW/LT-GaAs spacing of  $0.3$ ,  $0.8$ , and  $1.6 \mu\text{m}$ . Spectra have been shifted along vertical axis for visual clarity.

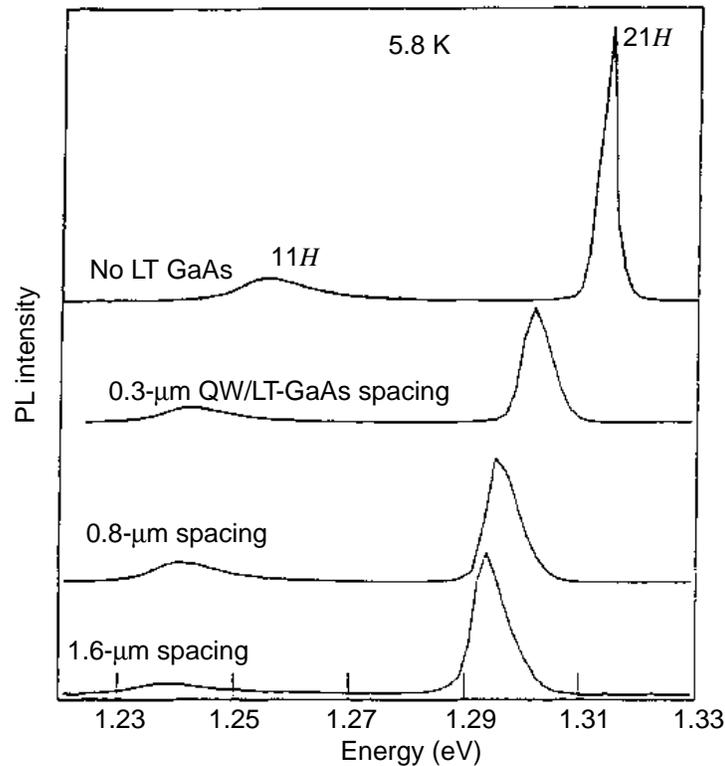

# Theory


We carried out self-consistent Schrödinger-Poisson calculations of the conduction and valence band energy levels and distribution of charge in this heterostructure using the boundary condition that at the NID-GaAs/LT-GaAs interface the Fermi level is pinned at 0.7 eV below the conduction band [14]. In our calculations the primary effect of the LT-GaAs layer is modeled by the Fermi level pinning at the NID-GaAs/LT-GaAs interface. We assume that the background doping in the NID GaAs is negligible, which means that the electrostatic electric field is constant across the NID-GaAs layer adjacent to the InGaAs QW. This electric field boundary condition varies for the different structures because of the variation in  $d$ . For the structure without an LT-GaAs layer, the electric field boundary condition is given by the midgap pinning of the Fermi level at the NID-GaAs/semi-insulating-GaAs substrate interface. We use the Hartree approximation for the valence band calculation, taking into account the increased bandgap of the strained InGaAs layer [15]; this calculation did not include many-body effects.

Our calculations confirm that the  $n = 1$  and  $n = 2$  conduction subbands are occupied, and good agreement with the magnetotransport-determined electron densities is obtained if the effective AlGaAs doping is  $4 \times 10^{18} \text{ cm}^{-3}$ . The calculated PL energies and oscillator strengths verify that we have observed the  $11H$  and  $21H$  transitions. We obtained excellent agreement between the observed and calculated values of  $11H$  and  $21H$  energies using the published strained bandgap renormalization parameters [15]. Our calculations confirm that, in comparison to the conduction subbands, the  $m = 1$  hole subband energy is insensitive to changes in the electric field in the NID GaAs.

Figure 2 shows the theoretical and experimental values of the  $11H$  and the  $21H$  PL energies as a function of the electric field in the NID GaAs. As confirmed by the good agreement between theory and experiment for the structures with LT GaAs, the observed decrease in the transition PL energies as  $d$  increases can be attributed to the quantum-confined Stark effect (QCSE), which has been observed before in undoped QWs in a  $p-i-n$  structure [11]. For our modulation-doped PHEMTs, the QCSE is caused by two opposing electric fields in the structure: the self-consistent electric field at the AlGaAs/InGaAs interface and the electric field in the NID-GaAs layer adjacent to the QW. The Fermi level pinning at the NID-GaAs/LT-GaAs interface results in a sample-to-sample variation of the electric field in the NID-GaAs layer, resulting in a blueshift in the  $11H$  and  $21H$  PL energies with increasing electric field in the NID GaAs.

The present theoretical model does not explain the large observed  $11H$  and  $21H$  PL energies of the sample with no LT GaAs. This disagreement could be due to a large error in the thickness of the NID-GaAs layer, a variation in the InGaAs composition, or a complicated doping profile in the NID GaAs and the semi-insulating GaAs buffer layers of the sample with no LT GaAs. Further experimental and possibly more theoretical work is needed to resolve this discrepancy.

Figure 2. Calculated and experimental  $11H$  and  $21H$  PL energies as a function of electric field in NID GaAs.

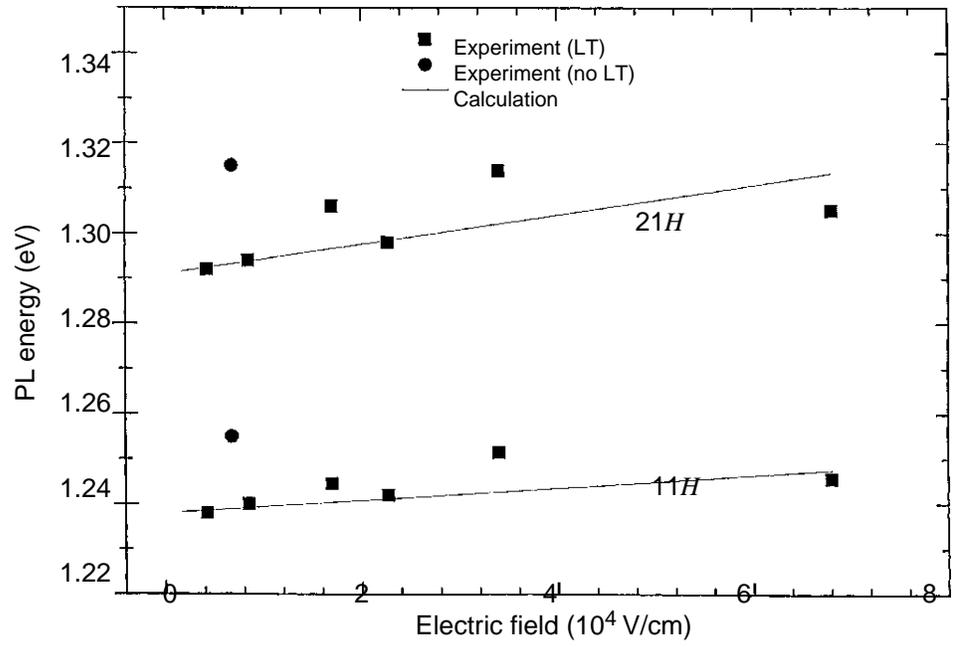

## Conclusion

In summary, low-temperature photoluminescence measurements on pseudomorphic modulation-doped transistors with a low-temperature GaAs layer in the GaAs buffer layer clearly show a decrease in the quantum-well PL transition energies compared to a structure with no LT GaAs. Self-consistent calculations of the electron and hole band structure confirm that the observed increasing redshift in PL energies with increasing QW/LT-GaAs spacing can be attributed to band bending induced by the Fermi level pinning at the NID-GaAs/LT-GaAs interface. These results are relevant to high-speed electronic and optoelectronic semiconductor devices, which use LT-GaAs buffer layers.

## Acknowledgement

The authors WDS and FHP acknowledge the support of U.S. Army Research Office contract DAAHO4-94-G-0153, National Science Foundation grant DMR-9414209, Professional Staff Congress/Board of Higher Education grant 666424, and the New York State Science and Technology Foundation through its Centers for Advanced Technology program.

## References

1. F. W. Smith, A. R. Calawa, C.-L. Chen, M. J. Manfra, and L. J. Mahoney, *IEEE Electron Devices Lett.* **9**, 77 (1988).
2. P. M. Solomon, S. L. Wright, and F. J. Canora, *IEEE Electron Devices Lett.* **12**, 117 (1991).
3. B. J.-F. Lin, C. P. Kocot, D. E. Mars, and R. Jaeger, *IEEE Trans. Electron Devices* **37**, 46 (1990).
4. M. Kaminska, Z. Liliental-Weber, E. R. Weber, T. George, J. B. Kortright, F. W. Smith, B.-Y. Tsaur, and A. R. Calawa, *Appl. Phys. Lett.* **54**, 1881 (1989).
5. M. O. Manasrech, D. C. Look, K. R. Evans, and C. E. Stutz, *Phys. Rev. B* **41**, 10,272 (1990).
6. D. C. Look, D. C. Walters, M. O. Manasrech, J. R. Sizelove, C. E. Stutz, and K. R. Evans, *Phys. Rev. B* **42**, 3578 (1990).
7. X. Liu, A. Prasad, W. M. Chen, A. Kurpiewski, A. Stoschek, Z. Liliental-Weber, and E. R. Weber, *Appl. Phys. Lett.* **65**, 3002 (1994).
8. A. C. Warren, J. M. Woodall, J. L. Freeouf, D. Grishchowsky, D. T. McInturff, M. R. Melloch, and N. Otsuka, *Appl. Phys. Lett.* **57**, 1331 (1990).
9. J. F. Whitaker, J. A. Valdmanis, M. Y. Frankel, S. Gupta, J. M. Chwalek, and G. A. Mourou, *Microelectron. Eng.* **12**, 369 (1990).
10. P. A. Folkes, Doran Smith, R. A. Lux, W. Zhou, R. Thompson, R. Moerkirk, and M. Lemeune, *Appl. Phys. Lett.* **69**, 2234 (1996).
11. D.A.B. Miller, D. S. Chemla, T. C. Damen, A. C. Gossard, W. Wiegmann, T. H. Wood, and C. A. Burrus, *Phys. Rev. B* **32**, 1043 (1985).
12. M. R. Melloch, D. C. Miller, and B. Das, *Appl. Phys. Lett.* **54**, 943 (1989).
13. S. K. Lyo and E. D. Jones, *Phys. Rev. B* **38**, 4113 (1988).
14. A. C. Warren, J. M. Woodall, P. D. Kirchner, X. Yin, X. Guo, F. H. Pollak, and M. R. Melloch, *J. Vac. Sci. Technol. B* **10**, 1904 (1992).
15. S. H. Pan, H. Shen, Z. Hang, F. H. Pollak, W. Zhuang, Q. Xu, A. P. Roth, R. Masut, C. LeCelle, and D. Morris, *Phys. Rev. B* **38**, 3375 (1988).

## Distribution

Admnstr  
Defns Techl Info Ctr  
Attn DTIC-OCP  
8725 John J Kingman Rd Ste 0944  
FT Belvoir VA 22060-6218

Dept of Defns  
Attn R222 J Fitz  
4800 Savage Rd  
FT Meade MD 20755-6000

Ofc of the Dir Rsrch and Engrg  
Attn R Menz  
Pentagon Rm 3E1089  
Washington DC 20301-3080

Ofc of the Secy of Defns  
Attn ODDRE (R&AT)  
Attn ODDRE (R&AT) S Gontarek  
The Pentagon  
Washington DC 20301-3080

OSD  
Attn OUSD(A&T)/ODDR&E(R) R J Trew  
Washington DC 20301-7100

AMCOM MRDEC  
Attn AMSMI-RD W C McCorkle  
Redstone Arsenal AL 35898-5240

CECOM  
Attn PM GPS COL S Young  
FT Monmouth NJ 07703

Dir for MANPRINT  
Ofc of the Deputy Chief of Staff for Prsnl  
Attn J Hiller  
The Pentagon Rm 2C733  
Washington DC 20301-0300

Hdqtrs Dept of the Army  
Assist Secy of the Army for RD&A  
Attn SARD-DOV H Fallin Rm 3E411  
The Pentagon  
Washington DC 20301-0103

US Army ARDEC  
Attn AMSTA-FSF-RE B95 N H A Jenkinson  
Picatinny Arsenal NJ 07806-5000

US Army Armament Rsrch Dev & Engrg Ctr  
Attn AMSTA-AR-TD M Fisette  
Bldg 1  
Picatinny Arsenal NJ 07806-5000

US Army CECOM  
Attn AMSEL-RD-ST-ST-TE L A Coryell  
FT Monmouth NJ 07703-5000

Director  
US Army CECOM Rsrch, Dev, & Engrg Ctr  
FT Monmouth NJ 07703-5201

US Army Edgewood RDEC  
Attn SCBRD-TD G Resnick  
Aberdeen Proving Ground MD 21010-5423

US Army Info Sys Engrg Cmnd  
Attn ASQB-OTD F Jenia  
FT Huachuca AZ 85613-5300

US Army Mis Cmnd  
Attn AMSMI-RD-WS P Ashley  
Attn AMSMI-RD-WS-PO J L Johnson  
Huntsville AL 35898

US Army Mis Cmnd Weapons Sci Dirctr  
Attn AMSMI-RD-WS-ST M J Bloemer  
Redstone Arsenal AL 35898-5358

US Army Natick RDEC Acting Techl Dir  
Attn SSCNC-T P Brandler  
Natick MA 01760-5002

Director  
US Army Rsrch Ofc  
Attn M Strocio  
4300 S Miami Blvd  
Research Triangle Park NC 27709

US Army Rsrch Ofc  
Attn H Everitt  
Attn J Harvey  
Attn M Dutta  
PO Box 12211  
Research Triangle Park NC 27709-2211

US Army Simulation, Train, & Instrmntn  
Cmnd  
Attn J Stahl  
12350 Research Parkway  
Orlando FL 32826-3726

## Distribution (cont'd)

US Army Tank-Automtv Cmnd Rsrch, Dev, &  
Engrg Ctr  
Attn AMSTA-TA J Chapin  
Warren MI 48397-5000

US Army Train & Doctrine Cmnd  
Battle Lab Integration & Techn Dirctrt  
Attn ATCD-B J A Klevecz  
FT Monroe VA 23651-5850

Nav Surface Warfare Ctr  
Attn Code B07 J Pennella  
17320 Dahlgren Rd Bldg 1470 Rm 1101  
Dahlgren VA 22448-5100

DARPA  
Attn B Kaspar  
3701 N Fairfax Dr  
Arlington VA 22203-1714

Physics Dept Hunter College of the City Univ  
of New York  
Attn G A Gumbs  
New York NY 10021

Physics Dept & New York State Ctr for  
Advanced Techn in Ultrafast Photonic  
Matr & Appl  
Attn F H Pollak  
Attn W D Sun  
Brooklyn College of the City Univ of NY  
Brooklyn NY 11210

Hicks & Associates, Inc  
Attn G Singly III  
1710 Goodrich Dr Ste 1300  
McLean VA 22102

Palisades Inst for Rsrch Svc Inc  
Attn E Carr  
1745 Jefferson Davis Hwy Ste 500  
Arlington VA 22202-3402

US Army Rsrch Lab  
Attn J Zavada  
PO Box 12211  
Research Triangle Park NC 27709-2211

US Army Research Lab  
Attn AMSRL-D R W Whalin  
Attn AMSRL-DD J Rocchio

US Army Research Lab (cont'd)  
Attn AMSRL-CI-LL Techn Lib (3 copies)  
Attn AMSRL-CS-AS Mail & Records Mgmt  
Attn AMSRL-CS-EA-TP Techn Pub (3 copies)  
Attn AMSRL-SE E Poindexter  
Attn AMSRL-SE H Leupold  
Attn AMSRL-SE J Mait  
Attn AMSRL-SE J Pellegrino  
Attn AMSRL-SE-DP H Brandt  
Attn AMSRL-SE-DS C Fazi  
Attn AMSRL-SE-E  
Attn AMSRL-SE-E D Wilmot  
Attn AMSRL-SE-E H Pollehn  
Attn AMSRL-SE-EE B Stann  
Attn AMSRL-SE-EE S Kennerly  
Attn AMSRL-SE-EE Z G Sztankay  
Attn AMSRL-SE-EI  
Attn AMSRL-SE-EI B Beck  
Attn AMSRL-SE-EI J Little  
Attn AMSRL-SE-EI M Tidrow  
Attn AMSRL-SE-EI N Dhar  
Attn AMSRL-SE-EI R Leavitt  
Attn AMSRL-SE-EI W Clark  
Attn AMSRL-SE-EM  
Attn AMSRL-SE-EM A Goldberg  
Attn AMSRL-SE-EM F Semendy  
Attn AMSRL-SE-EM G Euliss  
Attn AMSRL-SE-EM G Simonis  
Attn AMSRL-SE-EM J Pamulapati  
Attn AMSRL-SE-EM L Harrison  
Attn AMSRL-SE-EM M Stead  
Attn AMSRL-SE-EM M Taysing-Lara  
Attn AMSRL-SE-EM P Newman  
Attn AMSRL-SE-EM P Shen  
Attn AMSRL-SE-EM W Chang  
Attn AMSRL-SE-EM W Zhou  
Attn AMSRL-SE-EO  
Attn AMSRL-SE-EO G Wood  
Attn AMSRL-SE-EP  
Attn AMSRL-SE-EP B Zandi  
Attn AMSRL-SE-EP D Smith  
Attn AMSRL-SE-EP D Wortman  
Attn AMSRL-SE-EP J Bradshaw  
Attn AMSRL-SE-EP J Bruno  
Attn AMSRL-SE-EP J Pham  
Attn AMSRL-SE-EP K K Choi  
Attn AMSRL-SE-EP M Ferry

## Distribution (cont'd)

US Army Research Lab (cont'd)  
Attn AMSRL-SE-EP P Folkes (10 copies)  
Attn AMSRL-SE-EP R Tober  
Attn AMSRL-SE-EP S Rudin  
Attn AMSRL-SE-EP T B Bahder  
Attn AMSRL-SE-RE F Crowne  
Attn AMSRL-SE-RE S Tidrow  
Attn AMSRL-SE-RL  
Attn AMSRL-SE-RL A Lepore

US Army Research Lab (cont'd)  
Attn AMSRL-SE-RL C Scozzie  
Attn AMSRL-SE-RL K Jones  
Attn AMSRL-SE-RL M Dubey  
Attn AMSRL-SE-RL P Shah  
Attn AMSRL-SE-RL R Lareau  
Attn Chief AMSRL-SE  
Attn Chief AMSRL-SE-E  
Adelphi MD 20783-1197

<b>REPORT DOCUMENTATION PAGE</b>			<i>Form Approved</i> <i>OMB No. 0704-0188</i>	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
<b>1. AGENCY USE ONLY</b> (Leave blank)		<b>2. REPORT DATE</b> March 1999		<b>3. REPORT TYPE AND DATES COVERED</b> Final, 6/1/98-1/15/99
<b>4. TITLE AND SUBTITLE</b> Band-Bending Effect of Low-Temperature GaAs on a Pseudomorphic Modulation-Doped Field-Effect Transistor			<b>5. FUNDING NUMBERS</b>  DA PR: AH47 PE: 61102A	
<b>6. AUTHOR(S)</b> W. D. Sun, Fred H. Pollak (Brooklyn College, City University of New York), Patrick A. Folkes (ARL), Godfrey A. Gumbs (Hunter College, City University of New York)				
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b> U.S. Army Research Laboratory Attn: AMSRL-SE-EP                      email: pfolkes@arl.mil 2800 Powder Mill Road Adelphi, MD 20783-1197			<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b> ARL-TR-1933	
<b>9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b> U.S. Army Research Laboratory 2800 Powder Mill Road Adelphi, MD 20783-1197			<b>10. SPONSORING/MONITORING AGENCY REPORT NUMBER</b>	
<b>11. SUPPLEMENTARY NOTES</b> ARL PR: 9NENF1 AMS code: 611102.H47				
<b>12a. DISTRIBUTION/AVAILABILITY STATEMENT</b> Approved for public release; distribution unlimited.			<b>12b. DISTRIBUTION CODE</b>	
<b>13. ABSTRACT</b> (Maximum 200 words) Low-temperature photoluminescence (PL) measurements on pseudomorphic modulation-doped transistors with a low-temperature (LT) GaAs layer in the GaAs buffer layer clearly show a decrease in the quantum-well/PL transition energies compared to a structure with no LT GaAs. Self-consistent calculations of the electron and hole band structure confirm that the observed increase in the redshift in PL energies with increasing quantum-well/LT-GaAs spacing can be attributed to band bending induced by the Fermi level pinning at the undoped-GaAs/LT-GaAs interface.				
<b>14. SUBJECT TERMS</b> Quantum-confined Stark effect, semiconductor device			<b>15. NUMBER OF PAGES</b> 17	
			<b>16. PRICE CODE</b>	
<b>17. SECURITY CLASSIFICATION OF REPORT</b> Unclassified	<b>18. SECURITY CLASSIFICATION OF THIS PAGE</b> Unclassified	<b>19. SECURITY CLASSIFICATION OF ABSTRACT</b> Unclassified	<b>20. LIMITATION OF ABSTRACT</b> UL	

DEPARTMENT OF THE ARMY  
U.S. Army Research Laboratory  
2800 Powder Mill Road  
Adelphi, MD 20783-1197

An Equal Opportunity Employer