



A Model for Electron-Beam-Induced Current Analysis of mc-Si Addressing Defect Contrast Behavior in Heavily Contaminated PV Material

Preprint

Harvey Guthrey

Colorado School of Mines and National Renewable Energy Laboratory

Brian Gorman

Colorado School of Mines

Mowafak Al-Jassim

National Renewable Energy Laboratory

Gianluca Coletti

ECN Solar Energy

*Presented at the 2012 IEEE Photovoltaic Specialists Conference
Austin, Texas*

June 3–8, 2012

NREL is a national laboratory of the U.S. Department of Energy, Office of Energy Efficiency & Renewable Energy, operated by the Alliance for Sustainable Energy, LLC.

Conference Paper

NREL/CP-5200-54108

June 2012

Contract No. DE-AC36-08GO28308

NOTICE

The submitted manuscript has been offered by an employee of the Alliance for Sustainable Energy, LLC (Alliance), a contractor of the US Government under Contract No. DE-AC36-08GO28308. Accordingly, the US Government and Alliance retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy and its contractors, in paper, from:

U.S. Department of Energy
Office of Scientific and Technical Information

P.O. Box 62
Oak Ridge, TN 37831-0062
phone: 865.576.8401
fax: 865.576.5728
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce
National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
phone: 800.553.6847
fax: 703.605.6900
email: orders@ntis.fedworld.gov
online ordering: <http://www.ntis.gov/help/ordermethods.aspx>

Cover Photos: (left to right) PIX 16416, PIX 17423, PIX 16560, PIX 17613, PIX 17436, PIX 17721



Printed on paper containing at least 50% wastepaper, including 10% post consumer waste.

A Model for Electron-Beam-Induced Current Analysis of mc-Si Addressing Defect Contrast Behavior in Heavily Contaminated PV Material

Harvey Guthrey^{1,2}, Brian Gorman¹, Gianluca Coletti³, Mowafak Al-Jassim²

¹Colorado School of Mines, Golden, Colorado, United States

²National Renewable Energy Laboratory, Golden, Colorado, United States

³ECN Solar Energy, Petten, Netherlands

Abstract — Much work has been done to correlate electron-beam-induced current (EBIC) contrast behavior of extended defects with the character and degree of impurity decoration. However, existing models fail to account for recently observed contrast behavior of defects in heavily contaminated mc-Si PV cells. We have observed large increases in defect contrast with decreasing temperature for all electrically active defects, regardless of their initial contrast signatures at ambient temperature. This negates the usefulness of the existing models in identifying defect character and levels of impurity decoration based on the temperature dependence of the contrast behavior. By considering the interactions of transition metal impurities with the silicon lattice and extended defects, we attempt to provide an explanation for these observations. Our findings will enhance the ability of the PV community to understand and mitigate the effects of these types of defects as the adoption of increasingly lower purity feedstocks for mc-Si PV production continues.

Index Terms — mc-Si, silicon defects, electron beam induced current, EBIC contrast, iron contamination.

I. INTRODUCTION

EBIC contrast behavior of various types of extended defects, including grain boundaries, stacking faults, and dislocations, have been studied extensively [1-7]. Particular attention has been given to the temperature dependence of the EBIC contrast, as plots of contrast at dislocations (C_d) vs. temperature reveal information about extended defect character and impurity decoration[8-11]. There are several classifications of C_d vs. T behavior that have been previously described[11]. Type 1 behavior is represented by a positive slope and high contrast at room temperature and is related to high concentrations of deep level defects related to impurities and dislocation cores. Type 2 behavior is characterized by a negative slope and light or undetected contrast at room temperature. Light contrast at 300K increasing with decreasing temperature represents defects decorated with metallic impurities in the $10^4 - 10^6 \text{ cm}^{-1}$ range and shallow levels associated with strain. Type 2 defects showing little to no contrast at 300K are strain related or have concentrations of metallic impurities less than 10^4 cm^{-1} . Results of previous

studies of the EBIC contrast of various extended defects have generally agreed with this model. One study however, revealed a large increase in contrast, for decreasing T, at grain boundaries, showing both high and low contrast at 300K[12]. This behavior was attributed to the increase of the reduced surface recombination velocity associated with the different boundaries. However, experimental data with this trend has only been reported for grain boundaries.

II. EXPERIMENTAL

To formulate an EBIC contrast model addressing the issues associated with heavily contaminated mc-Si material, several samples were selected that were known to have concentrations of impurities that would be higher than the concentrations associated with traditional processing methods. The subject of the study was EG-Si that was intentionally contaminated with metallic impurities in the melt and processed into mc-Si PV cells. An uncontaminated EG-Si mc-Si PV cell was the control. The EBIC measurements were performed on a JEOL 5800 SEM equipped with a cold stage capable of achieving liquid nitrogen temperature.

III. RESULTS

EBIC images for the samples studied are shown in Fig. 1. The defects for which contrast measurement were taken are notated in both the images taken at 300K (a,c,e) and the images taken at 80K (b,d,f) and the results are summarized in Table 1. Figures 1a and 1b correspond to the EG-Si intentionally contaminated with 200ppm Fe in the melt, which is the most heavily contaminated specimen in this study. Two positions (1 and 2) were chosen, representing the traditional type 1 and type 2 room temperature contrasts. The contrast measurements at 80K reveal that both the areas measured exhibited large increases in contrast that deviate from the model. The contrast of the two defects measured from the sample contaminated with 50ppm Fe (Fig. 1c and 1d) does not have the same temperature dependent behavior. Mixed and lightly contaminated type 2 behavior fully describes the

defects present in these images. Figures 1e and 1f are from EG-Si not contaminated with any known impurities. The contrast measurements represent type 2 behaviors as expected.

The 200ppm Fe sample also exhibits strong contrast increases in regions not associated with the typical line features. There is no detectable contrast at room temperature, but at 80K the contrast is at levels associated with type 1 behavior. There is also a noticeable increase in contrast of the bulk material in the 50ppm Fe sample. The EG-Si sample did not have increased contrast in the bulk, suggesting that this effect is due to the Fe impurities.

Table 1. Summary of contrast measurements for the locations indicated in Figs. 1a-f.

Position	Contrast at 300K	Contrast at 80K
a,b-1	0.076	0.526
a,b-2	0.206	0.355
c,d-1	< 0.01	0.13
c,d-2	0.07	0.12
e,f-1	0.14	0.15
e,f-2	0.04	0.09

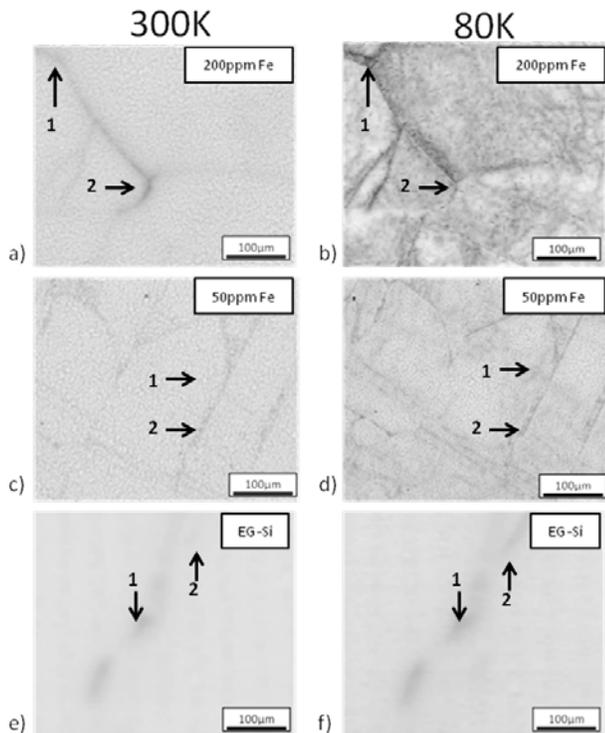


Fig. 1. EBIC images for a) 200ppm Fe sample b) 50ppm Fe sample, and c) EG-Si sample at 300K and 80K with positions for contrast measurements indicated.

IV. DISCUSSION

The EBIC contrast measurements summarized in Table 1 suggest a C_d vs. T relationship that is not fully described by the existing models. Using EG-Si and EG-Si with known concentrations of Fe added to the melt for the measurements suggests a strong dependence of the C_d vs. T behavior on contamination level. Both of the Fe-contaminated samples were taken from the top of a directionally solidified mc-Si ingot, so the concentration of Fe in each sample should be proportional to the amount added. However, the concentration of deep levels would be expected to increase with Fe contamination as the levels induced by Fe in interstitial positions, at grain boundaries and at dislocations, are deep in the bandgap[13]. If this is the case, then very strong contrast at all temperatures should be observed. However, the strongest contrasts are only observed at low temperatures. This behavior is typically understood as relating to the increased activity of shallow levels that become more active in the recombination process as temperatures decrease. However, the magnitude of the contrast increase suggests that another mechanism is responsible.

V. SUMMARY

Based on these results and their reproducible nature, a modification of existing models or a new model of the temperature dependence of EBIC contrast for defects in mc-Si is necessary. This new approach should take into account the observed large increases in contrast at low temperatures in the context of high concentrations of impurities. As the mc-Si PV industry moves toward lower purity feedstock, an EBIC contrast theory tailored to high concentrations of impurities is necessary to provide mc-Si PV producers the opportunity to address the variation in defect behavior associated with heavily contaminated material.

ACKNOWLEDGMENTS

Thanks to Manuel Romero, whose stimulating discussions on EBIC contrast made this work possible. This work was supported by the U.S. Department of Energy under Contract No. DE-AC36-08-GO28308 with the National Renewable Energy Laboratory.

REFERENCES

- [1] M. Beer, H. Menniger, H. Raidt et al., "On the analysis of EBIC contrast of crystal defects," *physica status solidi (a)*, vol. 61, no. 2, pp. 365-372, 1980.
- [2] L. Castellani, P. Gondi, C. Patuelli et al., "On the EBIC Contrast of Dislocations in Si," *physica status solidi (a)*, vol. 69, no. 2, pp. 677-685, 1982.
- [3] C. Donolato, "Theory of beam induced current characterization of grain boundaries in polycrystalline solar cells," *Journal of Applied Physics*, vol. 54, no. 3, pp. 1314-1322, 1983.

- [4] A. Ourmazd, P. Wilshaw, R., and G. Booker, R., "The temperature dependence of EBIC contrast from individual dislocations in silicon," *J. Phys. Colloques*, vol. 44, no. C4, pp. C4-289-C4-295, 1983.
- [5] A. Jakubowicz, "On the theory of electron-beam-induced current contrast from pointlike defects in semiconductors," *Journal of Applied Physics*, vol. 57, no. 4, pp. 1194-1199, 1985.
- [6] D. C., "The relation between EBIC contrast and recombination velocity of a grain boundary," *Materials Science and Engineering: B*, vol. 24, no. 13, pp. 61-63, 1994.
- [7] D. B. Holt, B. Raza, and A. Wojcik, "EBIC studies of grain boundaries," *Materials Science and Engineering: B*, vol. 42, no. 13, pp. 14-23, 1996.
- [8] A. Jakubowicz, U. H. Habermeier, A. Eisenbeiss et al., "Electron Beam Induced Current Versus Temperature Investigations of Localized Dislocations in Heat-Treated Czochralski Silicon," *physica status solidi (a)*, vol. 104, no. 2, pp. 635-641, 1987.
- [9] T. S. Fell, P. R. Wilshaw, and M. D. De Coteau, "EBIC investigations of dislocations and their interactions with impurities in silicon," *physica status solidi (a)*, vol. 138, no. 2, pp. 695-704, 1993.
- [10] M. Kittler, and W. Seifert, "On the origin of EBIC defect contrast in silicon. A reflection on injection and temperature dependent investigations," *physica status solidi (a)*, vol. 138, no. 2, pp. 687-693, 1993.
- [11] V. Kveder, M. Kittler, and W. Schrater, "Recombination activity of contaminated dislocations in silicon: A model describing electron-beam-induced current contrast behavior," *Physical Review B*, vol. 63, no. 11, pp. 115208, 2001.
- [12] O. F. Vyvenko, O. Kruger, and M. Kittler, "Cross-sectional electron-beam-induced current analysis of the passivation of extended defects in cast multicrystalline silicon by remote hydrogen plasma treatment," *Applied Physics Letters*, vol. 76, no. 6, pp. 697-699, 2000.
- [13] M. D. Dlamini, "Electrical/electronic effects of titanium and iron impurities in EFG and FZ solar cell silicon: SPV/EBIC analysis," *Solar Energy Materials and Solar Cells*, vol. 43, no. 4, pp. 353-361, 1996.